

Charge and orbital ordering in underdoped $\text{La}_{1-x}\text{Sr}_x\text{MnO}_3$

T. Mizokawa^{1,2}, D. I. Khomskii¹, and G. A. Sawatzky¹

¹*Solid State Physics Laboratory, Materials Science Centre, University of Groningen, Nijenborgh 4, 9747 AG Groningen, The Netherlands*

²*Department of Complexity Science and Engineering, University of Tokyo, Bunkyo-ku, Tokyo 113-0033, Japan*
(February 7, 2008)

We have explored spin, charge and orbitally ordered states in $\text{La}_{1-x}\text{Sr}_x\text{MnO}_3$ ($0 < x < 1/2$) using model Hartree-Fock calculations on d - p -type lattice models. At $x=1/8$, several charge and orbitally modulated states are found to be stable and almost degenerate in energy with a homogeneous ferromagnetic state. The present calculation indicates that a ferromagnetic state with a charge modulation along the c -axis which is consistent with the experiment by Yamada *et al.* might be responsible for the anomalous behavior around $x = 1/8$.

$\text{La}_{1-x}\text{Sr}_x\text{MnO}_3$ have extensively been studied because of its interesting magnetic and electric properties^{1,2}. An antiferromagnetic insulator LaMnO_3 evolves into a ferromagnetic metal with substitution of Sr for La or with hole doping². Underdoped $\text{La}_{1-x}\text{Sr}_x\text{MnO}_3$ with $x \sim 1/8$ which is located between the antiferromagnetic insulating region and the ferromagnetic metallic region, shows many anomalous behaviors²⁻⁶. $\text{La}_{0.875}\text{Sr}_{0.125}\text{MnO}_3$ is a paramagnetic insulator above T_{CA} (180 K) and has a canted antiferromagnetic state below it³. Recently, it has been found that $\text{La}_{0.875}\text{Sr}_{0.125}\text{MnO}_3$ becomes a ferromagnetic insulator below 140 K^{5,6}. One important question is why the hole-doped system can exist as an insulator. The superstructure observed by Yamada *et al.*⁴ indicates that charge ordering is responsible for the insulating behavior. However, it is still controversial whether charge ordering is realized in $\text{La}_{0.875}\text{Sr}_{0.125}\text{MnO}_3$ or not. Ahn and Millis studied the charge and orbital ordering in $\text{La}_{0.875}\text{Sr}_{0.125}\text{MnO}_3$ using a model of strong electron-lattice coupling limit and found that the charge ordering proposed by Yamada *et al.* can be reproduced using their model⁷. On the other hand, using the resonant x-ray scattering, Endoh *et al.* confirmed that the superlattice peak found by Yamada *et al.* does not show resonance at the Mn K -edge and concluded that there is no $\text{Mn}^{3+}/\text{Mn}^{4+}$ charge ordering in $\text{La}_{0.875}\text{Sr}_{0.125}\text{MnO}_3$ ⁶. Another interesting question is what is the origin of the ferromagnetism. Since the system is insulating, the simple double exchange mechanism cannot be applied. A model Hartree-Fock (HF) calculation for LaMnO_3 has predicted that, if the Jahn-Teller distortion is suppressed, a ferromagnetic insulating state with orbital ordering would be realized⁸. This means that the superexchange interaction between the Mn^{3+} ions can be ferromagnetic because of orbital ordering⁹. Endoh *et al.* observed orbital ordering below 145 K using x-ray scattering technique and argued that the orbital ordering is essential for the ferromagnetic and insulating state⁶. However, the orbital ordered state without charge ordering is expected to be metallic and may not be consistent with the fact that $\text{La}_{0.875}\text{Sr}_{0.125}\text{MnO}_3$ is insulating. In the doped manganites, the orbital modulation should couple with

the charge modulation in a similar way that the spin modulation couples with the charge modulation in the doped cuprates¹⁰. In order to understand the electronic structure of the ferromagnetic and insulating state in the doped manganites, it is necessary to consider the complicated interplay between the charge and orbital orderings. In this paper, we study possibility of charge and orbitally ordered states in underdoped $\text{La}_{1-x}\text{Sr}_x\text{MnO}_3$ using the model HF calculation and explore the origin of the ferromagnetic insulating state in underdoped $\text{La}_{1-x}\text{Sr}_x\text{MnO}_3$.

We use the multi-band d - p model with 16 Mn and 48 oxygen sites in which full degeneracy of Mn $3d$ orbitals and the oxygen $2p$ orbitals are taken into account⁸. The Hamiltonian is given by

$$H = H_p + H_d + H_{pd}, \quad (1)$$

$$H_p = \sum_{k,l,\sigma} \epsilon_k^p p_{k,l\sigma}^+ p_{k,l\sigma} + \sum_{k,l>l',\sigma} V_{k,ll'}^{pp} p_{k,l\sigma}^+ p_{k,l'\sigma} + H.c., \quad (2)$$

$$\begin{aligned} H_d = & \epsilon_d \sum_{i,m\sigma} d_{i,m\sigma}^+ d_{i,m\sigma} + u \sum_{i,m} d_{i,m\uparrow}^+ d_{i,m\uparrow} d_{i,m\downarrow}^+ d_{i,m\downarrow} \\ & + u' \sum_{i,m \neq m'} d_{i,m\uparrow}^+ d_{i,m\uparrow} d_{i,m'\downarrow}^+ d_{i,m'\downarrow} \\ & + (u' - j') \sum_{i,m>m',\sigma} d_{i,m\sigma}^+ d_{i,m\sigma} d_{i,m'\sigma}^+ d_{i,m'\sigma} \\ & + j' \sum_{i,m \neq m'} d_{i,m\uparrow}^+ d_{i,m\uparrow} d_{i,m\downarrow}^+ d_{i,m\downarrow} \\ & + j \sum_{i,m \neq m'} d_{i,m\uparrow}^+ d_{i,m\uparrow} d_{i,m'\downarrow}^+ d_{i,m'\downarrow}, \end{aligned} \quad (3)$$

$$H_{pd} = \sum_{k,m,l,\sigma} V_{k,lm}^{pd} d_{k,m\sigma}^+ p_{k,l\sigma} + H.c. \quad (4)$$

$d_{i,m\sigma}^+$ are creation operators for the $3d$ electrons at site i . $d_{k,m\sigma}^+$ and $p_{k,l\sigma}^+$ are creation operators for Bloch electrons with wave vector k which are constructed from the

m -th component of the $3d$ orbitals and from the l -th component of the $2p$ orbitals, respectively. The intra-atomic Coulomb interaction between the $3d$ electrons is expressed using Kanamori parameters, u , u' , j and j' ¹¹. The transfer integrals between Mn $3d$ and oxygen $2p$ orbitals $V_{k,lm}^{pd}$ are given in terms of Slater-Koster parameters ($pd\sigma$) and ($pd\pi$). The transfer integrals between the oxygen $2p$ orbitals $V_{k,lm}^{pp}$ are expressed by ($pp\sigma$) and ($pp\pi$). Here, the ratio ($pd\sigma$)/($pd\pi$) is -2.16. ($pp\sigma$) and ($pp\pi$) are fixed at -0.60 and 0.15, respectively, for the undistorted lattice. When the lattice is distorted, the transfer integrals are scaled using Harrison's law¹². The charge-transfer energy Δ is defined by $\epsilon_d^0 - \epsilon_p + nU$, where ϵ_d^0 and ϵ_p are the energies of the bare $3d$ and $2p$ orbitals and U ($= u - 20/9j$) is the multiplet-averaged $d-d$ Coulomb interaction. Δ , U , and ($pd\sigma$) for LaMnO₃ are 4.0, 5.5, and -1.8 eV, respectively, which are taken from the photoemission study¹³.

In Fig. 1, the energies of the spin, charge and orbitally ordered states are compared with those of the ferromagnetic and A -type antiferromagnetic states, which are plotted as functions of the hole concentration x . At x of 1/8, several charge ordered states exist as stable solutions. A schematic drawings of the ferromagnetic charge-ordered states are shown in Fig. 2. The unit cell consists of the four layers of $z = 0, 1/4, 1/2$, and $3/4$ along the c -axis. Each layer has four different Mn sites. In the charge-ordered states, the hole-rich planes ($z = 0$ and $1/2$) and the hole-poor planes ($z = 1/4$ and $3/4$) are alternately stacked along the c -axis. In the hole-poor plane, either $d_{3x^2-r^2}$ -like or $d_{3y^2-r^2}$ -like orbital is mainly occupied at each site and the $3x^2 - r^2/3y^2 - r^2$ -type orbital ordering. This orbital ordering in the hole-poor plane is essentially the same as that in LaMnO₃ although it is weak compared to that in LaMnO₃. While the orbital orderings at $z = 0$ and at $z = 3/4$ are out of phase for CO1 [see Fig. 2(a)], those are in phase for CO2 as shown in Fig. 2(b). Probably, the orbital ordering in the hole-poor plane is related to the observation by Endoh *et al.*⁶. In the hole-rich plane, for CO1, the Mn⁴⁺-like sites form a kind of stripe as shown in Fig. 2(a) and the extra holes are sitting at the oxygen sites between the Mn⁴⁺-like sites. For the CO2 state, the Mn⁴⁺-like sites form a square lattice and the extra holes are distributed at the oxygen sites surrounding the Mn⁴⁺-like site. The orbital ordering at the Mn³⁺-like sites in the hole-rich plane is very weak and depends on the orbital ordering in the hole-poor plane. These two ferromagnetic states with the charge and orbital modulations are degenerate in energy within the accuracy of the present calculation and are the lowest in energy among the charge-ordered states obtained in the present model calculations. Since LaMnO₃ is a charge-transfer-type Mott insulator, the Mn⁴⁺-like site has approximately four electrons. For example, in the CO1 state, The number of $3d$ electrons at the Mn³⁺-like sites in the hole-poor plane is ~ 4.08 and that of the Mn³⁺-like and the Mn⁴⁺-like sites in the hole-rich plane

are ~ 4.03 and ~ 4.01 , respectively. This calculated result can explain why the resonant x-ray scattering cannot distinguish between the Mn³⁺-like and Mn⁴⁺-like sites⁶.

These ferromagnetic states with the charge modulations are still metallic without lattice distortion. We have studied the effect of the lattice distortion which is shown in the right column of Fig. 3. The hole-poor plane ($z = 1/4$) can couple with the Jahn-Teller distortion of LaMnO₃. On the other hand, in the hole-rich plane ($z = 0$) for CO1, the shift of oxygen ion sitting between the Mn⁴⁺-like sites causes a doubling along the stripe of the Mn⁴⁺-like sites and is expected to open a band gap. Actually, we found that the small shift of these oxygens less than 0.1 Å (Fig. 3), which gives the superstructure along the c -axis and is consistent with the experiment by Yamada *et al.*⁴, can open a band gap for the two charge-modulated ferromagnetic states. The lattice distortion shown in Fig. 3 is enough to open a band gap for the CO2 state although the breathing-type distortion at the Mn⁴⁺-like sites is expected to be more effective. These ferromagnetic states with the lattice distortions are strong candidates for the ferromagnetic and insulating state found in La_{0.875}Sr_{0.125}MnO₃.

A sketch of the ferrimagnetic state accompanied by the charge and orbital ordering is shown in Fig. 4(a). In this arrangement, each hole-rich Mn⁴⁺-like site is surrounded by six hole-poor Mn³⁺ sites. This can be viewed as a lattice of orbital polaron¹⁴ which is displayed in Fig. 5(a). The superexchange interaction between the Mn³⁺-like and Mn⁴⁺-like sites is ferromagnetic and that between the Mn³⁺-like sites is antiferromagnetic in this ferrimagnetic state. The orbital polaron might be related to the ~ 12 Å magnetic clusters observed in La_{0.67}Ca_{0.33}MnO₃¹⁵. It is expected that the existence of this orbital polaron makes the magnetic interaction along the c -axis ferromagnetic and gives three-dimensional ferromagnetic coupling. Since the Mn³⁺-like sites should be accompanied by the Jahn-Teller distortion, the orbital polaron might also be related to the Jahn-Teller polaron observed in La_{1-x}Ca_xMnO₃ with $x < 0.5$ ¹⁶. On the other hand, in La_{1-x}Ca_xMnO₃ with $x > 0.5$, the number of Mn⁴⁺-like sites is larger than that of Mn³⁺-like sites. In such a case, the orbital polaron, in which a Mn⁴⁺-like site is surrounded by four Mn³⁺-like sites [see Fig. 5(b)], is expected to be relevant. This orbital polaron gives two-dimensional ferromagnetic coupling. Actually, it has been reported that Nd_{1-x}Sr_xMnO₃ with $x > 0.5$ has the A -type antiferromagnetic state, in which the ferromagnetic ab -planes are antiferromagnetically coupled along the c -axis¹⁷. This orbital polaron might be relevant in the A -type antiferromagnetic state of Nd_{1-x}Sr_xMnO₃.

At $x = 1/4$, the homogeneous ferromagnetic state is very stable and no ferromagnetic charge-modulated state was obtained. However, it is found that an antiferromagnetic state with charge and orbital ordering exists as a stable solution which is schematically shown in Fig. 4(b). This charge-ordered state can be viewed as a lattice of the orbital polaron coupled antiferromagnetically. Although

this state is higher in energy than the homogeneous ferromagnetic state as shown in Fig. 1, a lattice distortion of breathing type may stabilize the charge-ordered state relative to the ferromagnetic state.

There are two possible ways to describe the charge-ordered states: a polaron lattice language and a charge-density wave language. When the electron-lattice coupling term dominates the other terms, the polaron lattice picture is appropriate. The ferrimagnetic charge-ordered state obtained above can be viewed as a orbital polaron lattice and is expected to strongly couple with lattice distortions or the Jahn-Teller distortions. On the other hand, the charge-density-wave language becomes more appropriate when the kinetic energy term is relevant. It is natural to speculate that the electron-lattice coupling is weak in the ferromagnetic charge-modulated state compared to the orbital polaron lattice. The present calculation neglecting lattice distortions indicates that a kind of Umklapp process can give the modulation along the c -axis and that the charge-density-wave picture might be relevant in $\text{La}_{0.875}\text{Sr}_{0.125}\text{MnO}_3$. Since the number of $3d$ electrons at the Mn^{4+} -like site is almost the same as that of the Mn^{3+} -like site, the electron-lattice coupling is expected to be small. Actually the observed lattice modulation along the c -axis is very small⁴. This is also consistent with the experimental observation that resonant x-ray scattering fails to distinguish between Mn^{3+} -like and Mn^{4+} -like sites⁶. The present calculation fails to give a finite band gap without extra lattice distortion, suggesting that the weak electron-lattice coupling is still important to give the band gap. Here, it should be noted that a perfect nesting is not required in the present system because the Coulomb interaction term between the $3d$ electrons is very large and is comparable to the kinetic energy term and that, in this sense, the magnetic coupling between two Mn sites can be viewed as a kind of superexchange coupling.

In conclusion, we have studied possible charge and orbitally ordered states in underdoped $\text{La}_{1-x}\text{Sr}_x\text{MnO}_3$ using the model HF calculation. It has been found that the ferromagnetic state with the charge ordering along the c -axis, which is consistent with the experiment by Yamada *et al.*⁴, is stable at $x=1/8$. It has been argued that the charge and orbital ordering in the ferrimagnetic state can be interpreted as orbital polaron lattice. In order to clarify the interplay between the charge/orbital ordering and the lattice distortion, the underdoped manganites should be studied in future using a more realistic model which includes the electron-lattice interaction.

The authors would like to thank J. L. Garcia-Muñoz for useful discussions. This work was supported by the Netherlands Organization for Fundamental Research of Matter (FOM) and by the European Commission TRM network on Oxide Spin Electronics (OXSEN).

- ¹ J. B. Goodenough, Phys. Rev. **100**, 564 (1955); J. B. Goodenough and J. S. Zou, Nature **386**, 229 (1997).
- ² A. Urushibara, Y. Moritomo, T. Arima, A. Asamitsu, G. Kido, and Y. Tokura, Phys. Rev. B **51**, 14103 (1995).
- ³ H. Kawano, R. Kajimoto, M. Kubota, and H. Yoshizawa, Phys. Rev. B **53**, R14709 (1996).
- ⁴ Y. Yamada, O. Hino, S. Nohdo, R. Kanao, T. Inami, and S. Katano, Phys. Rev. Lett. **77**, 904 (1996).
- ⁵ R. Senis, V. Laukhin, B. Martínez, J. Fontcuberta, and X. Obradors, Phys. Rev. B **57**, 14680 (1998); S. Uhlenbruck, R. Teipen, R. Klingler, B. Büchner, O. Friedt, M. Hücher, H. Kierspel, T. Niemöller, L. Pinsard, A. Revcolevschi, and R. Gross, Phys. Rev. Lett. **82**, 185 (1999); M. Paraskevopoulos, J. Hemberger, A. Loidl, A. A. Mukhin, V. Yu. Ivanov and A. M. Balbashov, cond-mat/9812276.
- ⁶ Y. Endoh, K. Hirota, S. Ishihara, S. Okamoto, Y. Murakami, A. Nishizawa, T. Fukuda, H. Kimura, H. Nojiri, K. Kaneko, and S. Maekawa, Phys. Rev. Lett. **82**, 4328 (1999).
- ⁷ K. H. Ahn and A. J. Millis, Phys. Rev. B **58**, 3697 (1998).
- ⁸ T. Mizokawa and A. Fujimori, Phys. Rev. B **51**, 12880 (1995); Phys. Rev. B **54**, 5368 (1996).
- ⁹ K. I. Kugel and D. I. Khomskii, JETP Lett. **15**, 446 (1972); Usp. Fiz. Nauk. **136**, 621 (1981) [Sov. Phys. Usp. **25**, 231 (1982).]
- ¹⁰ W. Koshibae, Y. Kawamura, S. Ishihara, S. Okamoto, J. Inoue, and S. Maekawa, J. Phys. Soc. Jpn **66**, 957 (1997); V. I. Anisimov, I. S. Elfimov, M. A. Korotin, and K. Terakura, Phys. Rev. B **55**, 15494 (1997); T. Mizokawa and A. Fujimori, Phys. Rev. B **56**, R493 (1997).
- ¹¹ J. Kanamori, Prog. Theor. Phys. **30**, 275 (1963).
- ¹² W. A. Harrison, *Electronic structure and the Properties of Solids* (Dover, New York, 1989).
- ¹³ T. Saitoh, A. E. Bocquet, T. Mizokawa, H. Namatame, A. Fujimori, M. Abbate, Y. Takeda, and M. Takano, Phys. Rev. B **51**, 13942 (1995).
- ¹⁴ M. Paraskevopoulos, J. Hemberger, A. Loidl, A. A. Mukhin, V. Yu. Ivanov, and A. M. Balbashov, cond-mat/9812305; R. Kilian and G. Khaliullin, Phys. Rev. B **60**, 13458 (1999).
- ¹⁵ J. M. De Teresa, M. R. Ibarra, P. A. Algarabel, C. Ritter, C. Marquina, J. Blasco, J. Garcia, A. del Moral, and Z. Arnold, Nature **386**, 256 (1997).
- ¹⁶ A. Lanzara, N. L. Saini, M. Brunelli, F. Natali, A. Bianconi, P. G. Radaelli, and S.-W. Cheong, Phys. Rev. Lett. **81**, 878 (1998).
- ¹⁷ H. Kawano, R. Kajimoto, H. Yoshizawa, Y. Tomioka, H. Kuwahara, and Y. Tokura, Phys. Rev. Lett. **78**, 4253 (1997).

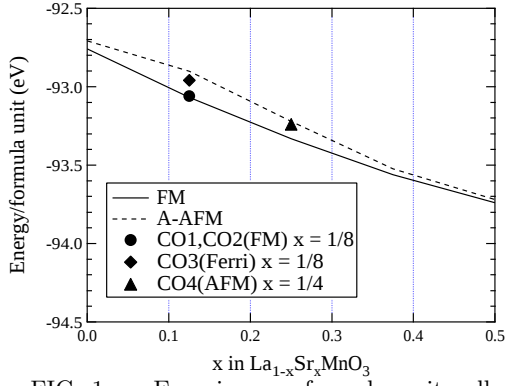


FIG. 1. Energies per formula unit cell of the various charge-ordered states, the ferromagnetic state (solid curve), and the *A*-type antiferromagnetic state (dashed curve) as functions of hole concentration x .

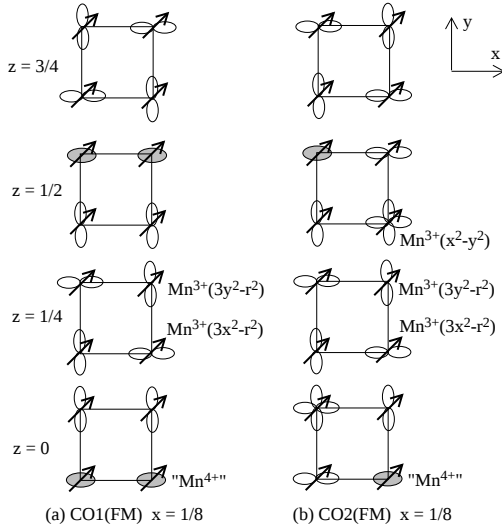


FIG. 2. Schematic drawings of the charge and orbital orderings for the ferromagnetic state at $x=1/8$. The unit cell consists of four layers of $z=0, 1/4, 1/2$, and $3/4$, each of which have four Mn sites. The arrows indicate spin directions at each site and the shaded orbitals are for Mn^{4+} -like hole-rich sites.

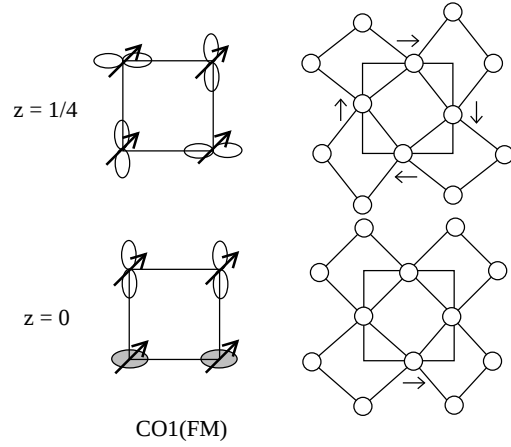


FIG. 3. Schematic drawings of the charge and orbital orderings (left column) and the lattice distortions (right column) for the hole-rich ($z=0$) and hole-poor ($z=1/4$) planes in the ferromagnetic state. The open circles and the arrows indicate the oxygen ions and the shifts of the oxygen ions, respectively.

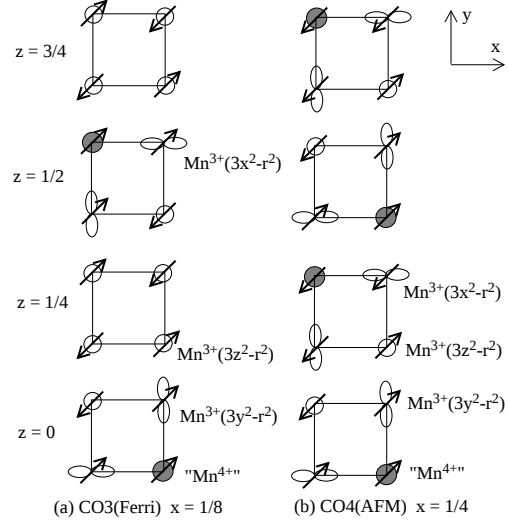


FIG. 4. Schematic drawings of the charge and orbital orderings (a) for the ferrimagnetic states at $x=1/8$ and (b) for the antiferromagnetic state at $x=1/4$. The unit cell consists of four layers of $z=0, 1/4, 1/2$, and $3/4$, each of which have four Mn sites. The arrows indicate spin directions at each site and the shaded orbitals are for Mn^{4+} -like hole-rich sites.

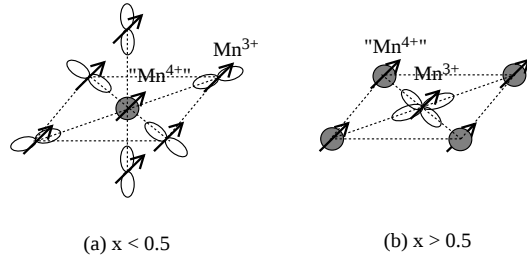


FIG. 5. Schematic drawings of the orbital polarons (a) for $x < 0.5$ and (b) for $x > 0.5$. The arrows indicate spin directions at each site and the shaded orbitals are for Mn^{4+} -like hole-rich sites.